


DEVELOPMENT OF MICROPLANE MODEL OF CONCRETE
WITH PLURAL TYPES OF GRANULAR PARTICLES

(Reprinted from Transaction of JSCE, Vol.433/V-15, Aug. 1990)



Ahmed M. FARAHAT

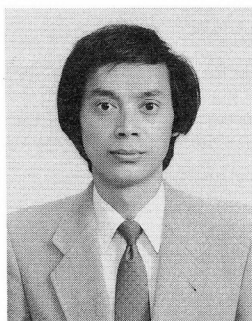

Zhishen WU



Tada-aki TANABE

SYNOPSIS

A fracture or damage model for monotonic behavior of concrete using microplane mechanism is developed. The microplane is defined as the contact surface between particles inside the material. In this study, concrete is idealized to contain two types of particles which are aggregate and mortar particles. This is in contrast to the Bazant's single particle model. It is assumed that the normal stress on the microplane of any orientation within the material is a function of the normal strain on the same microplane. This strain is assumed to be equal to the resolved components of the macroscopic strain tensor. In addition, shear strains on the same microplanes are considered. The model can represent experimentally observed macroscopic behavior of concrete under the effect of different types of loading conditions.

Keywords : concrete, fracture, softening, microplane, aggregate and mortar.

A. M. Farahat is a Doctoral Student of Civil Engineering at Nagoya University, Nagoya, Japan. He received his Master Degree from University of Cairo, Egypt. His research interests include failure mechanism of concrete structures. He is a member of JSCE and JCI.

Z. Wu is an Assistant Professor of Civil Engineering at Nagoya University, Nagoya, Japan. He received his Doctor of Engineering Degree from University of Nagoya in 1990. His research interests include computational modelling, failure mechanism and cracking properties of RC structures. He is a member of JSCE and JCI.

T. Tanabe is a Professor of Civil Engineering at Nagoya University, Nagoya, Japan. He received his Doctor of Engineering Degree from University of Tokyo. He is the chairman of JCI Committee on the Thermal Stress of Massive Concrete Structures besides a member of various committees of JSCE, JCI and ACI. His main research is directed to the dynamic failure mechanism of RC structures besides the thermal stress.

1. INTRODUCTION

In investigating the characteristics of concrete, which is composed of granulates in brittle cement past matrix, a large research effort has been devoted to its constitutive modeling. The commonly used are the macroscopic models such as classical plastic models, deformation theory models, fracture models and continuum damage models. Despite of the significant initial success during the last 20 years, however, the macroscopic approach showed gradually its limitations. As pointed by Bazant et al.[3], [4], probably only relatively minor further improvement can be expected depending on the expanding experimental data. The main reason is the difficulty to deal in general with the microcracking and the actual failure of microstructure due to the fact that the microcracking make characteristics of concrete of a very complex nature with dilatancy, strain localization, softening and all other sorts of nonlinear phenomena. We can not expect to model all these aspects of the material by unified general theory, although some investigators recently tried to introduce microscopic consideration or damage parameters due to microcracking to the macroscopic models (Mazar[11], Wu and Tanabe[12]). Analyzing the material through the micromechanism seems to be rational and powerful because it enables us to look into far insight of the true damage or failing mechanisms of concrete under the effect of different types of monotonic and repeated loading. For these reasons, it appears preferable to describe the behavior of the material not globally but individually for the contacts between the particles of various orientation within the material and then superimpose the contribution from all the contact planes.

Micromechanical models were also analyzed for different kinds of materials such as metals, concrete and granular materials. Routhenburg et al.[1], [2], Chang et al.[5], [6] and Christofersen et al.[7] investigated the micromechanical behavior of granular materials. In their studies, only one kind of particle and one kind of contact were considered. Bazant et al.[3], [4], used the microplane model to obtain tensile strain softening curves of concrete. In his model, concrete has been assumed to have only one kind of microplane, which exists at the contact surfaces between aggregates. This assumption is not practically true because the main source of the damage or softening is the spreading of the microcracks into the mortar through the contact surface between aggregate and mortar. Moreover, in his analysis, only the normal microstrain was considered and an additional volumetric elastic strain was introduced to adjust the value of Poisson's ratio.

In the present study, as a continuation of modeling concrete through the microstructure, the development of the microplane model is investigated. To represent the different kinds of microplanes, concrete is idealized to have two types of particles, which are aggregate and mortar particles.(refer to Fig. 1). This idealization helps us to investigate the micromechanical behavior not only on the contact between aggregates but also on the contact between aggregate and mortar. In addition, to explain the behavior more reasonably, shear strain on the microplane is considered. The current formulation has been shown to be capable of modeling the available macroscopic data of concrete.

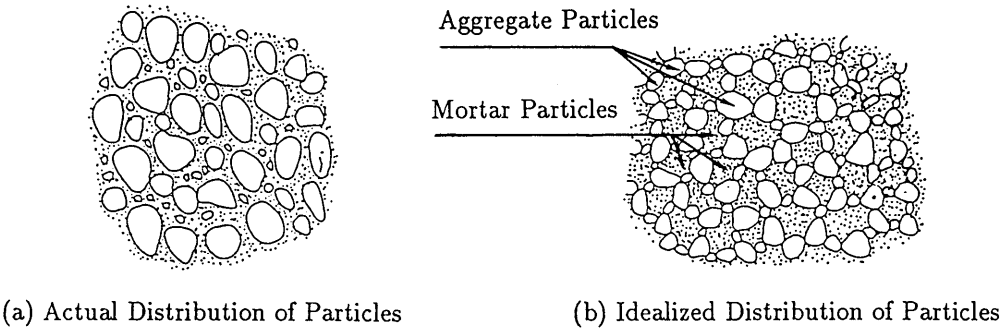


Fig. 1 Distribution of Particles in Concrete

2. THEORETICAL CONSIDERATION

2.1 GENERALIZATION AND IDEALIZATION

The overall macroscopic stress in concrete is examined by considering the contact forces that transmitted by the contacting particles at the microscale. Concrete is idealized to be composed of two types of particles which are aggregate and mortar particles. In addition, every mortar particles is assumed to be surrounded by a specified number of aggregate particles as illustrated in Fig. 1(b).

2.2 AVERAGE STRESS TENSOR FROM AVERAGES OF CONTACT FORCES

If a region v is subjected to an incremental stress of $\Delta\sigma_{ij}$ and the stress state of this region is in equilibrium, the average stress increment $\Delta\bar{\sigma}_{ij}$ is defined [1], [2], [5] and [7] as:

$$\Delta\bar{\sigma}_{ij} = \frac{1}{v} \int_v \Delta\sigma_{ij} dv \quad (1)$$

Using Eq.(1), the average stress increment for aggregate and mortar particles is written as :

$$\Delta\bar{\sigma}_{ij}^a = \frac{1}{v^a} \int_{v^a} \Delta\sigma_{ij} dv \quad (2)$$

$$\Delta\bar{\sigma}_{ij}^m = \frac{1}{v^m} \int_{v^m} \Delta\sigma_{ij} dv \quad (3)$$

where, v^a and v^m are the volume of an aggregate particle and a mortar particle, respectively. Using the equilibrium condition (i.e. $\Delta\sigma_{ij,j} = 0$) and the divergence theory, the volume average integral in Eq.(1) can be converted into surface integral. The average incremental stress $\Delta\bar{\sigma}_{ij}$ is reduced as follows:

$$\Delta\bar{\sigma}_{ij} = \frac{1}{v} \int_v \Delta\sigma_{ij} dv = \frac{1}{v} \int_v \Delta\sigma_{ik} x_{j,k} dv = \frac{1}{v} \int_s \Delta\sigma_{ik} x_j n_k ds = \frac{1}{v} \int_s \Delta t_i x_j ds \quad (4)$$

where, v is the volume of the particle, s is the boundary surface of the particle, x_j is the coordinates of a point on s , n_k is the normal on s at x_j and Δt_i is the traction on s at x_j as shown in Fig. 2(a). For a finite number of contact points, the surface integral of the boundary contact forces increments can be replaced by the summation of these contact forces increments. Eq.(4) can then be written in the form :

$$\Delta\bar{\sigma}_{ij} = \frac{1}{v} \sum_{m=1}^n \Delta f_i^m x_j^m \quad (5)$$

where, n is the number of contacts per particle, x_j is the contact vector (position vector) for m^{th} contact and Δf_i is the contact force increment at the m^{th} contact. The contact vector can be measured from the centroid of the particle to the contact point [1], [2], [5] and [6]. The average stress increment within the aggregate and mortar particles can be represented as :

$$\Delta\bar{\sigma}_{ij}^a = \frac{1}{v^a} \sum_{\alpha_1} \Delta f_i^{\alpha_1} l_j^{\alpha_1} \quad (6)$$

$$\Delta\bar{\sigma}_{ij}^m = \frac{1}{v^m} \sum_{\alpha_2} \Delta f_i^{\alpha_2} l_j^{\alpha_2} \quad (7)$$

where, α_1 and α_2 are the notation to identify each contact point along the boundary of the aggregate and mortar particles, respectively. Terms Δf_i^α and l_j^α refer to the scalar components of the contact forces increments Δf^α and contact vectors l^α at the contact locations (refer to Fig.2(b) and (c)).

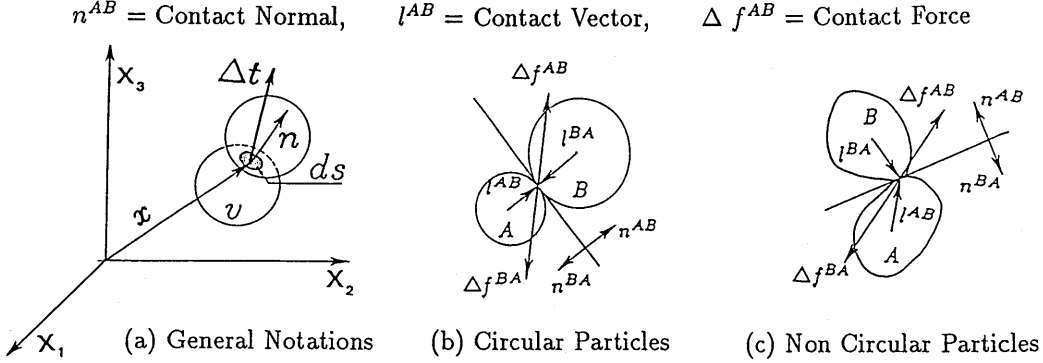


Fig. 2 Contact Force, Contact Normal and Contact Vector

Furthermore, we will use volume average to define the incremental mean stress for any representative volume by summing the stresses increments for all particles within this volume as follows :

$$\Delta \bar{\sigma}_{ij} = \frac{1}{V} \sum_a \Delta \bar{\sigma}_{ij}^a v^a + \frac{1}{V} \sum_m \Delta \bar{\sigma}_{ij}^m v^m \quad (8)$$

Eq.(8) can be simplified to

$$\Delta \bar{\sigma}_{ij} = \frac{1}{V} \left[\sum_{C_1} \Delta f_i^{C_1} l_j^{C_1} + \sum_{C_2} \Delta f_i^{C_2} l_j^{C_1} + \sum_{C_2} \Delta f_i^{C_2} l_j^{C_2} \right] \quad (9)$$

where, C_1 is the total number of contacts between aggregate particles, C_2 is the total number of contacts between aggregate and mortar particles, V is the total volume. This equation is for large but finite number of particles. In Eq.(9), the first part, which represents the contribution of contacts due to aggregates has two components. That is because of the assumption that every aggregate particle have two different kinds of contact points, which are the contacts between two aggregates and the contact between an aggregate and mortar particles. On the other hand, the second part of that equation which represents the contribution of the mortar has only one component because we have assumed that only one kind of contact exists around every mortar particle. This single contact is between aggregate and mortar particles.

The total number of contacts do not take into account the orientation of the contact normals. Because the case of two dimensional system is considered in the current study, a function $E(\theta)$ which considers the relative frequency of contacts with different orientations of normals will be defined. The number of contacts with normals between θ and $\theta + \Delta\theta$ will be $CE(\theta)\Delta\theta$. This function satisfies the next expression :

$$\int_0^{2\pi} E(\theta) d\theta = 1 \quad (10)$$

For isotropic granular assemblies, Rothenburg [1],[2] defined the orientational distribution function $E(\theta)$ as :

$$E(\theta) = \frac{1}{2\pi} \quad (11)$$

Since the current study is restricted to isotropic material, the definition proposed by Rothenburg[1], [2] will be used.

Unfortunately, the calculation of the average incremental stress tensor using Eq.(9) requires exact knowledge of contact forces increments and contact vector terms for all particles. Equivalent simpler expressions can be developed by considering certain averages of grouped information. If the contacts are grouped within a finite number of orientational intervals, then, the grouped averages $\Delta \bar{f} \bar{l}(\theta)$ in Eq.(9) can be calculated. Assuming that the number of contacts is very large, while the orientational interval $\Delta\theta$ is very small, Eq.(9) can be expressed in the next form :

$$\Delta \bar{\sigma}_{ij} = \frac{1}{V} \left[\sum_{\theta_g} \Delta \bar{f}_i^{C_1} \bar{l}_j^{C_1}(\theta) (C_1 E(\theta) \Delta\theta) + \sum_{\theta_g} \Delta \bar{f}_i^{C_2} \bar{l}_j^{C_1}(\theta) (C_2 E(\theta) \Delta\theta) + \sum_{\theta_g} \Delta \bar{f}_i^{C_2} \bar{l}_j^{C_2}(\theta) (C_2 E(\theta) \Delta\theta) \right] \quad (12)$$

For finite but large number of particles, the average incremental stress tensor from the discrete information is an accurate analogue to the incremental stress tensor of continuum mechanics and we will assume that $\Delta \bar{\sigma}_{ij} = \Delta \sigma_{ij}$. In the case of isotropic analysis (i.e. $\bar{l}_j(\theta) = \bar{l}_n(\theta)$ and $E(\theta) = 1/2\pi$), Eq.(12) can be written in the next integral form :


$$\Delta \sigma_{ij} = \frac{C_1 \bar{l}_1}{V} \int_0^{2\pi} \Delta \bar{f}_i^{C_1}(\theta) n_j^{C_1}(\theta) E(\theta) d\theta + \frac{C_2 \bar{l}_1}{V} \int_0^{2\pi} \Delta \bar{f}_i^{C_2}(\theta) n_j^{C_1}(\theta) E(\theta) d\theta + \frac{C_2 \bar{l}_2}{V} \int_0^{2\pi} \Delta \bar{f}_i^{C_2}(\theta) n_j^{C_2}(\theta) E(\theta) d\theta \quad (13)$$

where, $\bar{l}_1$ is the average radius of aggregates and $\bar{l}_2$ is the average radius of mortar particles, which can be obtained by assuming that every mortar particles is surrounded by n particles of aggregates (refer to Fig.(1)).


2.3 RELATION BETWEEN AVERAGE CONTACT FORCES AND STRAIN TENSOR

Neglecting the possible rotation between particles, the average contact force is linked with the contact displacement using the linear contact law as follows :

$$\Delta f_n^c = K_n \Delta \left(\frac{\delta l_n^c}{l} \right), \quad \Delta f_s^c = K_s \Delta \left(\frac{\delta l_t^c}{l} \right) \quad (14)$$

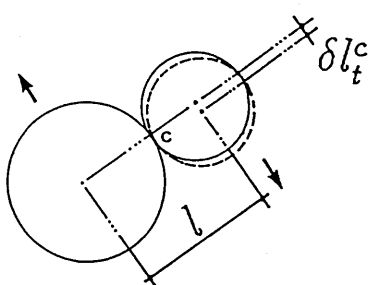

(a) Shear Contact Displacement

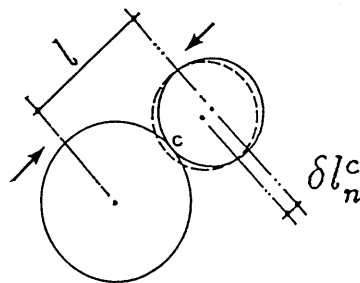

(b) Normal Contact Displacement

Fig. 3 Contact Displacement Components

where $(\delta l_n^c/l)$ represents the relative normal displacement between particle centers ; $(\delta l_t^c/l)$ is the relative tangent displacement at the contact ; l is the distance between particle centers in contact. These terms are illustrated in Fig.3. K_n and K_s refer to the normal and shear stiffnesses of the contact, while, Δf_n and Δf_s are the components of the contact force increments. Eq. (13) for the average stress tensor contains only the averages of forces of the same orientation. Therefore, it is necessary to equate these averages of forces to quantities describing average displacement components for similarly oriented contacts.

If $\bar{\delta}_n^c(\theta)$ and $\bar{\delta}_t^c(\theta)$ are the average normal and shear displacements for a groups of contacts having the same orientation, thus, Eq.(14) can take the next form:

$$\Delta \bar{f}_n^c(\theta) = K_n \Delta \bar{\delta}_n^c(\theta), \quad \Delta \bar{f}_s^c(\theta) = K_s \Delta \bar{\delta}_t^c(\theta) \quad (15)$$

where,

$$\Delta \bar{\delta}_n^c(\theta) = \Delta \left(\frac{\delta \bar{l}_n(\theta)}{\bar{l}} \right), \quad \Delta \bar{\delta}_t^c(\theta) = \Delta \left(\frac{\delta \bar{l}_t(\theta)}{\bar{l}} \right) \quad (16)$$

Here, we will assume that the normal and shear microstrains $(\varepsilon_n, \varepsilon_t)$, which govern progressive cracking and failure of microplane are equal to the resolved components of the macroscopic strain tensor on the same microplane , i.e.

$$\varepsilon_n = \frac{\delta l_n}{l} = \varepsilon_{ij} n_i n_j, \quad \varepsilon_t = \frac{\delta l_t}{l} = \varepsilon_{ij} t_i n_j \quad (17)$$

In which n are the direction cosines of the unit normal of the microplane and t are the direction cosines of the unit tangent of the microplane i.e., $n = (\cos\theta, \sin\theta)$ and $t = (-\sin\theta, \cos\theta)$. It can be expected that Eq.(17) will hold true when expressed as averages taken over the microplanes of similar orientations. It is reasonable to expect that:

$$\Delta \bar{\delta}_n^c(\theta) = \Delta \left(\frac{\delta \bar{l}_n(\theta)}{\bar{l}} \right) = \phi(\Delta \varepsilon_{ij} n_i n_j), \quad \Delta \bar{\delta}_t^c(\theta) = \Delta \left(\frac{\delta \bar{l}_t(\theta)}{\bar{l}} \right) = \phi(\Delta \varepsilon_{ij} t_i n_j) \quad (18)$$

where, ϕ is a function of ε_{ij} and the direction cosines.

2.4 STRESS - STRAIN RELATIONSHIP

If the average normal and tangential contact forces in Eq.(15) are combined with Eq.(18) and the resulting value is introduced into Eq.(13), we can obtain the following incremental stress - strain relation:

$$\Delta \sigma_{ij} = D_{ijkl} \Delta \varepsilon_{kl} \quad (19)$$

where,

$$D_{ijkl} = \frac{C_1 \bar{l}_1 \phi \bar{a}_1}{2\pi V} \int_0^{2\pi} (k_n n_i n_j n_k n_l + k_s t_i n_j t_k n_l) C_1 d\theta + \frac{C_2 \bar{l}_1 \phi \bar{a}_2}{2\pi V} \int_0^{2\pi} (k_n n_i n_j n_k n_l + k_s t_i n_j t_k n_l) C_2 d\theta + \frac{C_2 \bar{l}_2 \phi \bar{a}_2}{2\pi V} \int_0^{2\pi} (k_n n_i n_j n_k n_l + k_s t_i n_j t_k n_l) C_2 d\theta \quad (20)$$

where $\bar{a}_1$ and $\bar{a}_2$ are the averages of contact areas between aggregates alone and between aggregate and mortar particles, respectively. k_n and k_s are the normal and shear stiffnesses which can be obtained through the stress - strain relationship of the microplane. Because of the lack of experimental data which can distinguish the behavior of different contacts, all contacts will be assumed to have the same properties in the current study. Eq.(20) can be simplified to:

$$D_{ijkl} = \eta \int_0^{2\pi} (k_n a_{ijkl} + k_s b_{ijkl}) d\theta \quad (21)$$

where,

$$\eta = \frac{\phi}{2\pi} \left[\frac{C_1 \bar{l}_1 \bar{a}_1}{V} + \frac{C_2 \bar{l}_1 \bar{a}_2}{V} + \frac{C_2 \bar{l}_2 \bar{a}_2}{V} \right]$$

$$a_{ijkl} = n_i n_j n_k n_l, \quad b_{ijkl} = t_i n_j t_k n_l$$

2.5. NORMAL AND SHEAR STIFFNESSES OF MICROPLANE (i.e. k_n, k_s)

Normal stiffness of the microplane is taken as the ratio between the incremental microplane normal stress and normal strain, while, shear stiffness is defined as the ratio between the incremental microplane shear stress and shear strain as follows :

$$k_n = \frac{d\sigma_n}{d\varepsilon_n}, \quad k_s = \frac{d\tau_{nt}}{d\varepsilon_{nt}} \quad (22)$$

where σ_n and ε_n are the normal stress and the normal strain on the microplane, while, τ_{nt} and ε_{nt} are the shear stress and the shear strain on the same microplane. Here, we made an assumption that k_s is related to k_n in the form :

$$k_s = \lambda k_n \quad (23)$$

where, λ is constant. This assumption will be valid in both tension and compression.

2.6 NORMAL STRESS - STRAIN RELATION ON THE MICROPLANE

2.6.1 MICROPLANES IN TENSION

Since the normal microstress and the normal microstrain relation governs the progressive development of cracking on the microplane of any orientation, and since our aim is to describe softening, damage and the real failure of the microstructure, at which σ_n reduces to zero, σ_n as a function of ε_n must first rise up to the maximum limit, then, must decrease gradually up to zero. Hence, the following expression is assumed if $\varepsilon_n \geq 0$:

$$\sigma_n = E_n \varepsilon_n e^{-k_t \varepsilon_n^p} \quad (24)$$

Where, E_n , k_t and p are positive constants.

2.6.2 MICROPLANES IN COMPRESSION

In the same manner, the next expression for microplane in compression (i.e. if $\varepsilon_n \leq 0$) is assumed:

$$\sigma_n = E_n \varepsilon_n e^{-k_c |\varepsilon_n|^{p_1}} \quad (25)$$

where, E_n , k_c and p_1 are also positive constants.

3. THEORETICAL DERIVATION OF POISSON'S RATIO AND THE RELATIONSHIP BETWEEN INITIAL MACRO AND MICROSTIFFNESSES

To check the value of Poisson's ratio, the case of uniaxial strain is considered (i.e. $\varepsilon_x = 0$ and $\varepsilon_y \neq 0$). Assuming that for small strains $\sigma_n = E_n \varepsilon_n$, $k_n = E_n$ and $k_s = \lambda k_n$, the following results can be obtained by using Eqs.(19) and (21):

$$\sigma_x = \eta E_n \int_0^{2\pi} (\sin^2(\theta) \cos^2(\theta) - \lambda \sin^2(\theta) \cos^2(\theta)) d\theta \varepsilon_y = \eta E_n (1 - \lambda) \frac{\pi}{4} \varepsilon_y \quad (26)$$

$$\sigma_y = \eta E_n \int_0^{2\pi} (\sin^4(\theta) + \lambda \sin^2(\theta) \cos^2(\theta)) d\theta \varepsilon_y = \eta E_n (3 + \lambda) \frac{\pi}{4} \varepsilon_y \quad (27)$$

Thus, $\sigma_x/\sigma_y = (1 - \lambda)/(3 + \lambda)$ and, in view of Hook's law of $\sigma_x/\sigma_y = \nu/1 - \nu$, the relation between ν and λ is obtained as follow :

$$\nu = \frac{1 - \lambda}{4} \quad (28)$$

Since the elastic Poisson ratio of concrete is around 0.20, λ is suggested to be 0.20. In addition, from Eq.(27), the relation between the initial macroscopic and microscopic elastic stiffnesses E and E_n can be observed as follow :

$$E = \left[\frac{\pi}{4} (3 + \lambda) \eta \right] E_n \quad (29)$$

where, η is a material parameter. This parameter, as defined in Eq.(21), depends on the size of particles, contact areas, number of contacts, and the total volume. The value of this parameter will be selected to obtain a consistent values between the initial stiffnesses of the macroscopic experimental data and that of the microplanes.

4. NUMERICAL IMPLEMENTATION AND COMPARISON WITH THE TEST DATA

To insure the capability of the current model and to calibrate its results, different types of plane problems are examined, in which, these plane problems are subjected to several types of loading conditions. The results are compared with the available macroscopic test data as shown below

4.1 UNIAXIAL TENSION

In the beginning the microstiffness of the contacts, E_n , is obtained using Eq.(29). In Eq.(29), the values of $\lambda = 0.20$ and $\eta = 1.0$ are used. Then, the values of the parameters k_t and p of the model which can describe the tensile behavior of the microplanes have been found to fit the experimental data of Evans and Marathe[8]. A careful attention has been made to obtain identical initial stiffnesses, peak stresses, and a reasonable hardening and softening tendencies. The other parameters for compressive microplanes k_c and p_1 are kept constant. The fits illustrated in Fig.4. In these figures, concrete has different characteristics. According to the experimental data, the peak stresses of concretes shown in Fig.4 from a to f are 16.14, 15.60, 21.10, 21.40, 26.70 and 31.70 kgf/cm^2 , respectively. The values of $10^{-4} E$ (E is the initial macrostiffness) of these concrete are 15.50, 16.50, 17.50, 20.0, 15.25, and 13.5 kg/cm^2 , respectively. In Fig.4, the current model is shown by the solid lines, while, the dashed lines represent the experimental data[8]. For all cases constant values of $p = 1.5$, $p_1 = 2.0$ and $k_c = 20 \times 10^4$ are used. The values of $10^{-4} E_n$ for concretes shown in Fig.4 from (a) to (f), are 6.17 , 6.565, 6.963, 7.96, 6.068 and 5.37 kgf/cm^2 , respectively, and those of $10^{-4} k_t$ are 29.5 , 34.7, 24.0, 28.4, 13.3 and 8.70 . As seen, a reasonable agreement with the test data is achieved. It should be noted that, we have used only one parameter, k_t , to determine a good fitting with the test data. Through this small number of data, we try to obtain the relation between k_t values and macroscopic compressive strength and Young's modulus. Finally the obtained relation is shown in Fig.5. From Fig.5, it can be noticed that, as the compressive strength of concrete increases, the value of k_t decreases. This may be due to the fact that the stress strain relationship for high strength concrete, which is almost linear up to the fracture limit, is followed by a sudden drop of stress. This sudden drop occurs due to the highly softening phenomena which is controlled by the k_t parameter.


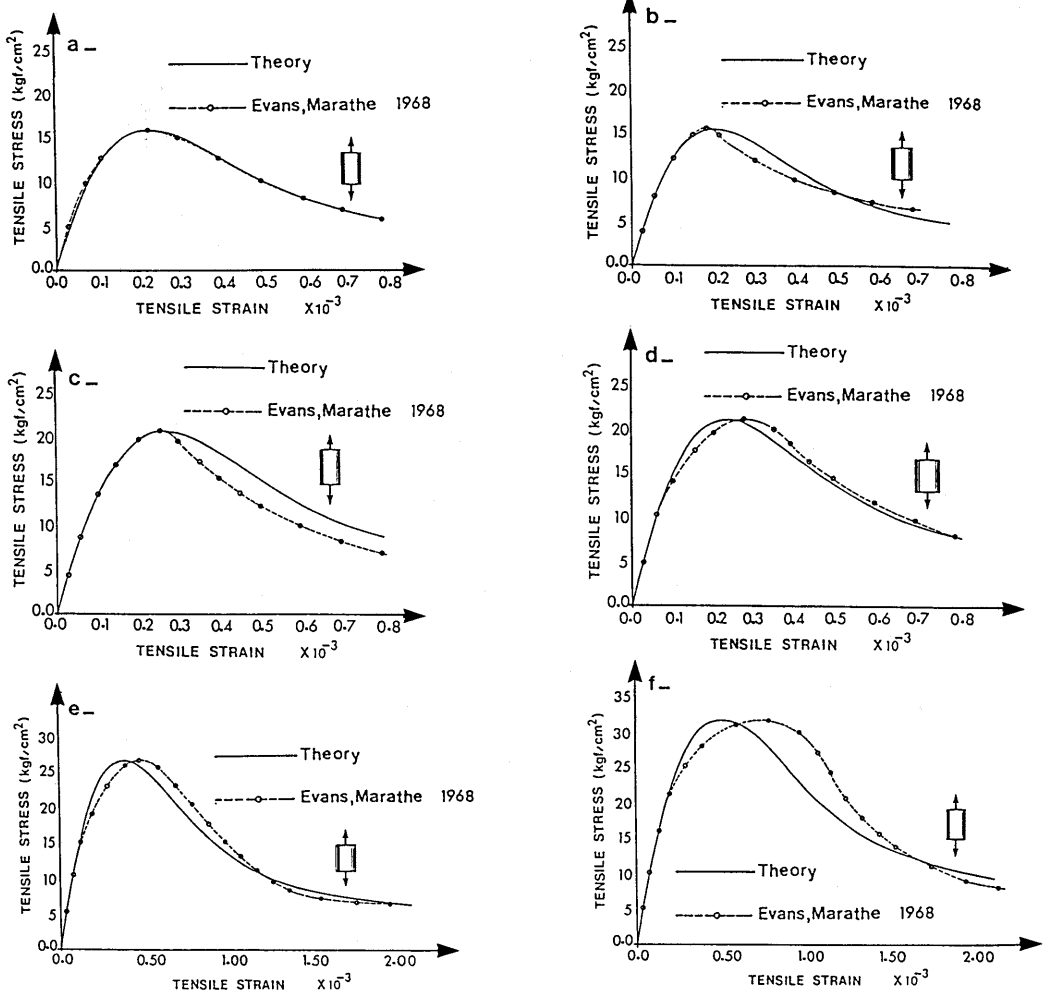


Fig. 4 Fits of Current Study to Test Data of Evans et al.[8]

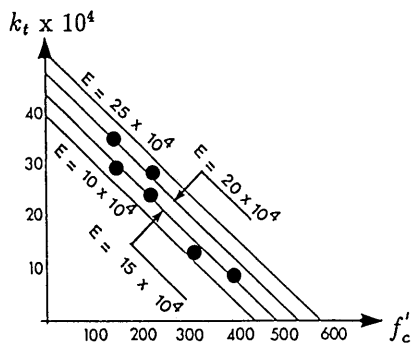

$$k_t = a f'_c + b E + c$$

$$a = -882.1, \quad b = 0.814 \quad \text{and} \quad c = 3.1 \times 10^5$$

f'_c = Comp. Strength of Concrete

E = Young's Modulus

f'_c and E are in kg/cm^2

Fig. 5 The Relationship between (k_t), and (f'_c) for Different Values of (E)

4.2 UNIAXIAL COMPRESSION

In the same manner, in the beginning, E_n , is obtained using Eq.(29). In this equation, the values of $\lambda = 0.20$ and $\eta = 1.0$ are used. The parameters p_1 and k_c have been obtained to get a good fits of the data of Desayi et al.[9] and Kupfer et al.[10], as shown in Fig.6 . For all cases, $p = 1.5$, $k_t = 26 \times 10^4$ and $p_1 = 2.0$ are used. The values of $10^{-4} E_n$ for concretes a, b, c and d are 8.22 , 13.08, 20.0 and 10.98 kgf/cm^2 , and those of $10^{-4} k_c$ are 18.8, 22.2, 19.6, and 13.8. As can be seen, a good agreement with the experimental data is obtained, although, all parameters are fixed constant except k_c . Here again, the relation between k_c values and macroscopic compressive strength of concrete and Young's modulus were obtained and shown in Fig.7. From that figure, it is noticed that the variation of k_c due to the increase of the compressive strength of concrete is not too much. This may be due to the fact that a sudden failure occurs in all examined cases just after the peak stress. This sudden failure means that the softening phenomena which are governed by the parameter k_c are almost the same.

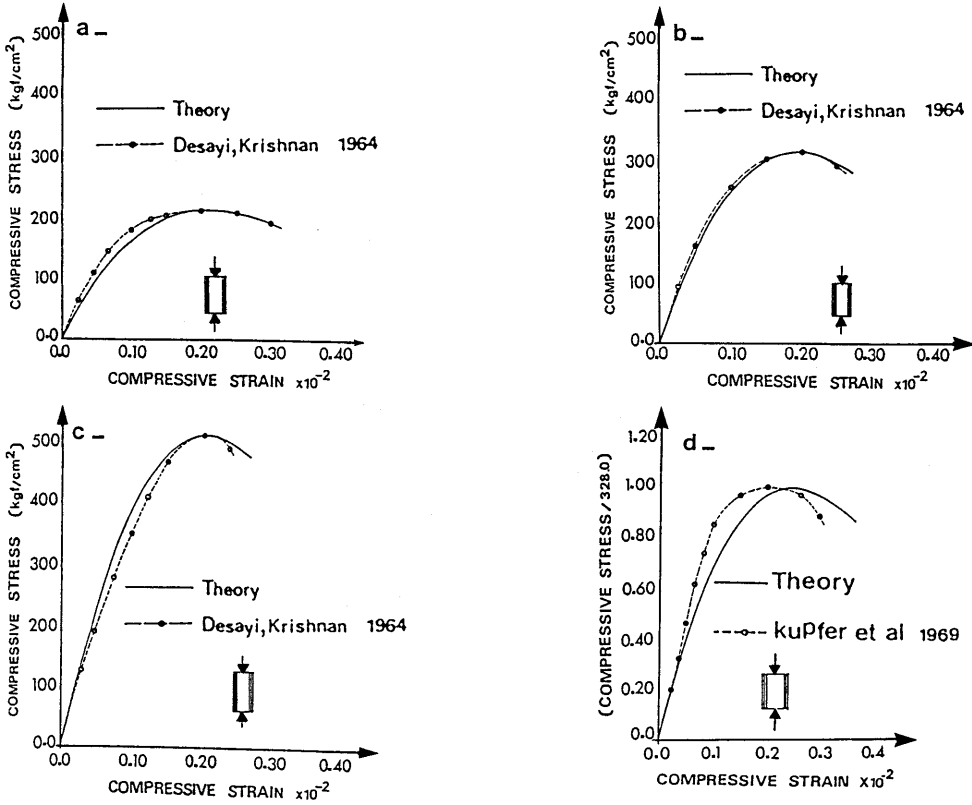


Fig. 6 Fits of Present Study to Test Data of References[9] and [10]

4.3 BIAXIAL LOADING

In Fig.8, the comparison between the model results and test data of Kupfer et al[10] are presented. A reasonable agreement of fitting the test data is obtained. In Fig.8, the following values of the parameters are used, $\eta = 1.0$, $\lambda = 0.20$, $p = 1.5$, $p_1 = 2.0$, $k_t = 24.5 \times 10^4$, $k_c = 13.8 \times 10^4$ and $E_n = 10.80 \times 10^4$ kgf/cm^2 . These values are obtained to satisfy the uniaxial behavior(tension and compression) and obtained from the proposed relations of k_t and k_c .

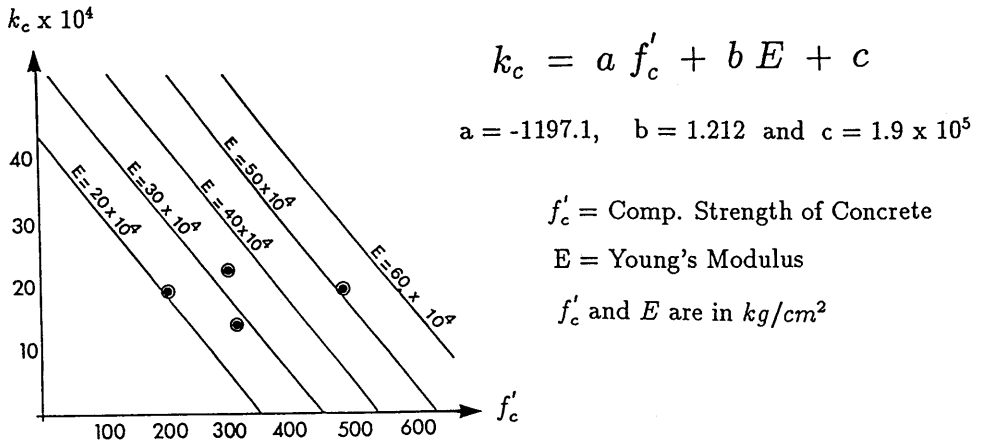


Fig. 7 The Relationship between (k_c), and (f'_c) for Different Values of (E)

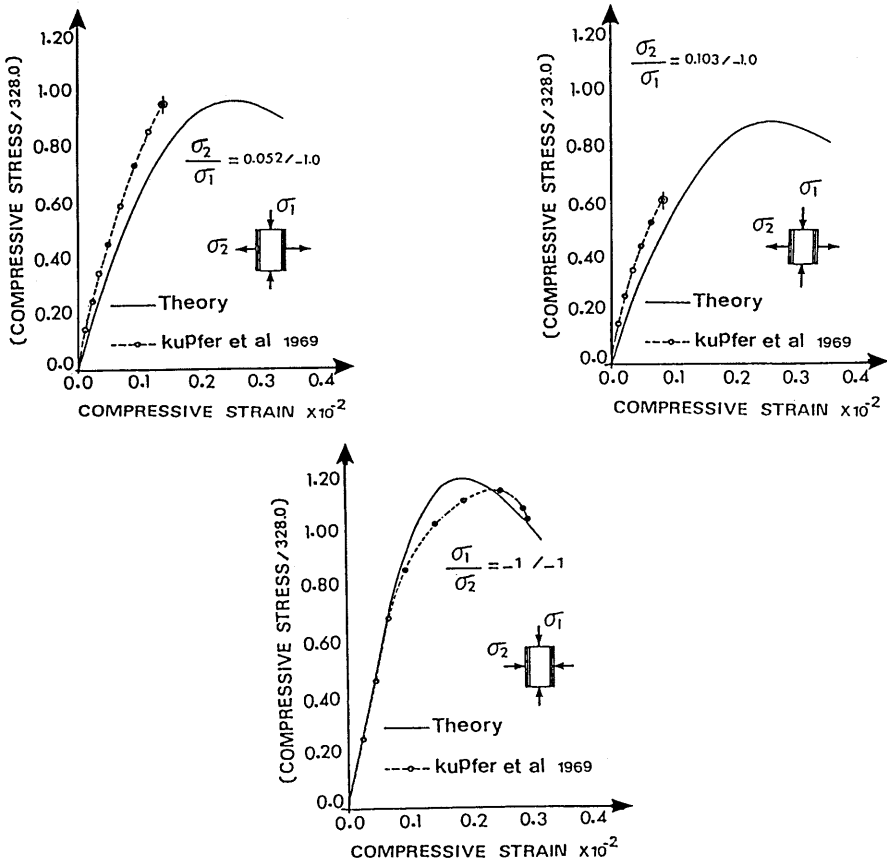


Fig. 8 Fits of Present Study to Test Data of Reference[10]

5. CONCLUSIONS

The monotonic behavior of plain concrete is investigated. The microplane model is analyzed to recognize the actual damage or failure of the microstructure under the effect of different types of loading conditions. The analysis is based on the micromechanical behavior of granular materials. Furthermore, to represent the different types of contacts in the material, plain concrete is idealized to have two types of particles (aggregates and mortar). This idealization enables us to study the actual micromechanism not only between the aggregates as investigated before in the previous research work but also on the contact between mortar and aggregates. It can be concluded that:

- (1) Progressive fracture or damage of concrete due to microcracking can be described using the microplane model.
- (2) Through the proposed model, the relation between the initial macroscopic and microscopic stiffnesses can be obtained.
- (3) The macroscopic elastic Poisson's ratio is found to give the ratio between the shear stiffness and the normal stiffness of microplane.
- (4) The proposed model, considering only one kind of microplane, is found to be consistent with the experimental data. However, this model can also consider two kinds of microplanes, but, experimental data are necessary to distinguish the behavior of the different microplanes. Also, a more comprehensive research must be conducted to study the density distribution, the nonuniformity of strain distribution, and the cyclic behavior of microplane to have a better understanding of the characteristics of the microstructure.

ACKNOWLEDGMENT

The authors are pleased to acknowledge staffs and students in the concrete laboratory of department of civil engineering, Nagoya University, for their help in preparing this report.

REFERENCES

- (1) Bathurst, R.J. and Rothenburg, L.: Observations on Stress-Fabric Relationships in Idealized Granular Materials, *Journal of mechanics of materials*, Vol.9, 1990, pp.65-80.
- (2) Bathurst, R.J. and Rothenburg, L.: Micromechanical Aspects of Isotropic Granular Assemblies with Linear Contact Interactions, *Journal of Applied Mechanics*, ASME, Vol.55, March, 1988, pp.17-23.
- (3) Bazant, Z. P. and Oh, A. M.: Microplane Model for Progressive Fracture of Concrete and Rock, *Journal of Engineering Mechanics*, ASCE, No.4, April, 1985, pp.559-582.
- (4) Bazant, Z. P. and Gambarova, P. G.: Crack Shear in Concrete: Crack Band Microplane Model, *Journal of Structural Engineering*, ASCE, Vol.110, September, 1984, pp.2015-2035.
- (5) Chang, C. S.: Strain Tensor and Deformation for Granular Materials, *Journal of Engineering Mechanics*, ASCE, Vol.116, No.4, April, 1990, pp.790-804.
- (6) Chang, C. S. and Misa A.: Theoretical and Experimental Study of Regular Packings of Granulars, *Journal of Engineering Mechanics*, ASCE, Vol.115, No.4, April, 1989, pp.704-720.

- (7) Christoffersen , J. , Mehrabadi , M. M. and Nemat Nasser ,S.: A Micromechanical Description of Granular Material Behavior, Journal of Applied Mechanics , ASME , Vol.48 ,1981 ,pp.339 - 344.
- (8) Evans , R. H. and Marathe, M. S.: Microcracking and Stress - Strain Curves for Concrete in Tension, Materials and Structures (Paris) , No.1 , Jan.- Feb. , 1968 , pp.61-64.
- (9) Desayi ,P. and Krishnan, S.: Equation for Stress - Strain Curve of Concrete, Journal of the American Concrete Institute , ACI , March , 1964 , pp.345 - 350.
- (10) Kupfer ,H. and Hilsdorf, H. K.: Behavior of Concrete Under Biaxial Stresses, Journal of the American Concrete Institute, ACI, August , 1969 , pp.656-666.
- (11) Mazar, J.: A Description of Micro - and Macroscale Damage of Concrete Structures, Engineering Fracture Mechanics, 1986, Vol.25, pp. 729 - 737.
- (12) Wu, Z. S., and Tanabe, T.: A Hardening - Softening Model of Concrete Subjected to Compressive Loading, Journal of Structural Engineering, Architectural Institute of Japan, 1990, Vol.36B, pp. 153 - 162 .